



STANDARD EXTRUSION TOLERANCES

TABLE 1: WIDTH TOLERANCES

<u>DIMENSION</u>	<u>NOMINAL DESIGN TOLERANCES</u> FOR THE FOLLOWING TYPES OF DIMENSIONS (SEE ILLUSTRATIONS BELOW)	
<u>WIDTH</u>	<u>NORMAL WIDTH</u> (NORMAL TOLERANCES)	<u>WIDTH EQUALS SUM OF SEVERAL SPACES</u> (WIDER TOLERANCES REQUIRED)
	Dimension "W" (Fig. 1) is not affected by changes in the size of other width dimensions and is therefore easier to control.	Dimension "W" (Fig. 2) is equal to the sum of the spaces "A", "B", "C" & "D". Changes in the size of any of the individual spaces affects the width dimension, thus making it harder to control.
INCHES		
From To	\pm	\pm
0 1	.020	.030
1 2	.030	.045
2 4	.040	.060
4 6	.050	.075
6 10	.060	.090
10 15	.075	.100
15 20	.090	.125
20 24	.125	.150
NOTE: The nominal tolerances are design tolerances. Once a part has been developed, the running tolerances can usually be tighter than the design tolerances. Running tolerances normally must be \pm the actual measurements obtained for development samples.		

Dimension "W" is not directly dependent on spaces "A" through "D" as the reference dimension "REF" can float. It is therefore easier to control than the "W" dimension in fig. 2 and NORMAL TOLERANCES CAN BE USED.

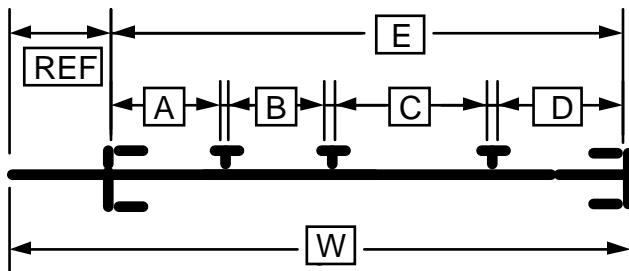


FIG. 1: NORMAL WIDTH

Dimension "W" is equal to the sum of the spaces "A" + "B" + "C" + "D" and is directly affected by changes to these dimensions. It is therefore more difficult to control than the "W" dimension in fig. 1. and WIDER TOLERANCES ARE REQUIRED. (Dimension "E" in fig. 1 also is equal to the sum of the spaces.)

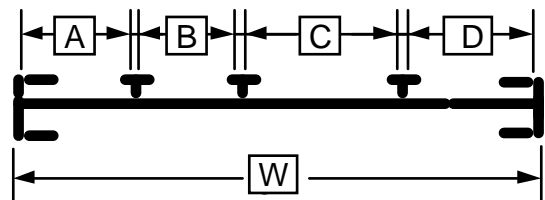


FIG. 2: WIDTH = THE SUM OF SEVERAL SPACES

TABLE 2: LEG LENGTH & HEIGHT DESIGN TOLERANCES

<u>DIMENSION</u>	<u>NOMINAL DESIGN TOLERANCES</u> <u>FOR THE FOLLOWING TYPES OF DIMENSIONS (SEE ILLUSTRATIONS BELOW)</u>	
<u>LEG LENGTH OR HEIGHT</u>	<u>SINGLE SEGMENTS</u> (NORMAL TOLERANCES)	<u>SUM OF SEVERAL SEGMENTS</u> (WIDER TOLERANCES REQUIRED)
INCHES	Dimension "L" (Fig. 3) is for a single segment. The size of this segment is not dependent or affected by changes in the size of other dimensions and is easier to control.	Dimension "C" (Fig. 4) is for two or more segments ("L"). Changes in the size of any of the individual segments affects this dimension. This type of dimension is harder to control.
From To	±	±
.125	.010	-----
.125 .250	.015	.020
.250 .500	.020	.030
.500 1.0	.025	.040
1.0 1.5	.030	.045
1.5 2.0	.040	.060
2.0 3.0	.045	.070
3.0 4.0	.050	.075
4.0 6.0	.060	-----
6.0 8.0	.075	-----
8.0 10.0	.090	-----

NOTE: The nominal tolerances are design tolerances. Once a part has been developed, the running tolerances can usually be tighter than the design tolerances. Running tolerances normally must be ± the actual measurements obtained for development samples.

Dimension "L" is for a single segment. It is not dependent or affected by changes in the size of other dimensions and easier to control than those in fig. 4. NORMAL TOLERANCES CAN BE USED.

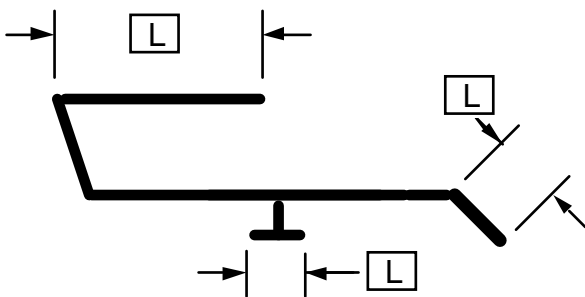


FIG. 3: LENGTH OR HEIGHT IS A SINGLE SEGMENT

Dimension "C" is the sum of the segments "L" and is affected by changes in these dimensions. It is therefore more difficult to control "C" than the "L" dimensions in fig. 3. and WIDER TOLERANCES ARE REQUIRED.

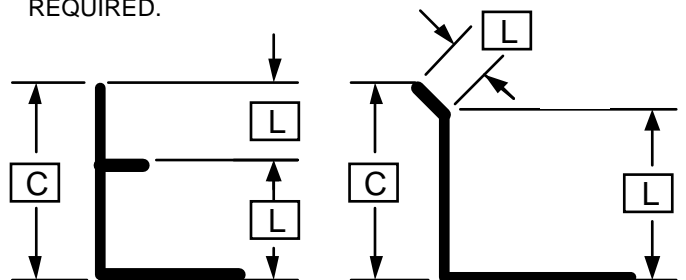


FIG. 4: SUM OF SEVERAL SEGMENT LENGTHS

TABLE 3: SPACE & GAP TOLERANCES

<u>DIMENSION</u>	<u>NOMINAL DESIGN TOLERANCES</u> FOR THE FOLLOWING TYPES OF DIMENSIONS (SEE ILLUSTRATIONS BELOW)		
<u>SPACES & GAPS</u>	<u>GAP OR SINGLE SPACE</u> (NORMAL TOLERANCES)	<u>MULTIPLE SPACES</u> (WIDER TOLERANCES REQUIRED)	<u>ADJUSTABLE GAP</u> (TIGHTER TOLERANCES POSSIBLE)
	Dimensions "S" or "G" (Fig. 5) are not affected by changes in the size of other dimensions and are therefore easier to control.	Dimensions "A", "B", "C" & "D" (Fig. 6) are multiple spaces that control width "W". The greater the number of spaces, the wider the tolerances should be for the individual spaces.	Dimension "G" (Fig. 7) can be adjusted by moving the top leg up or down instead of having to change dimension "S". If this is allowable, tighter tolerances are possible.
INCHES			
From To	±	±	±
.060 .080	15 %	-----	-----
.080 .125	10%	-----	-----
.125 .250	10%	-----	.015
.250 .500	.025	.030	.015
.500 1.0	.025	.035	.020
1.0 2.0	.030	.045	.020
2.0 3.0	.040	.050	-----
3.0 4.0	.045	.060	-----
NOTE: The nominal tolerances are design tolerances. Once a part has been developed, the running tolerances can usually be tighter than the design tolerances. Running tolerances normally must be ± the actual measurements obtained for development samples.			

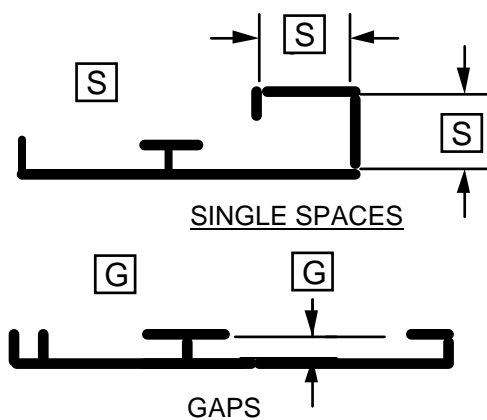


FIG. 5: SINGLE SPACES & GAPS

Dimensions "A" + "B" + "C" + "D" are multiple spaces that control the width "W". The greater the number of spaces, the more difficult it is to control the "W" dimension and to hold all the individual spaces within spec. WIDER TOLERANCES ARE REQUIRED for the spaces as well as the width.



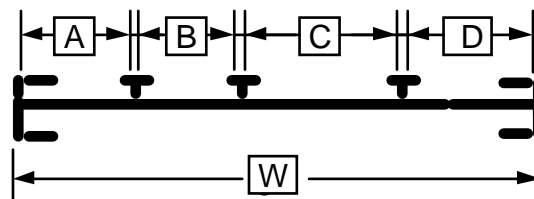


FIG 6 : MULTIPLE SPACES

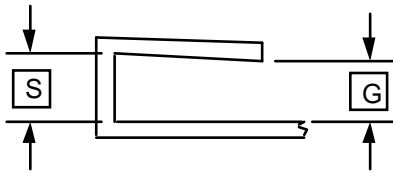


EXAMPLE OF AN ADJUSTABLE GAP

If the part is designed with the space "S" slightly greater than the gap "G", the top leg can be moved up or down slightly to adjust the gap dimension while running the part.

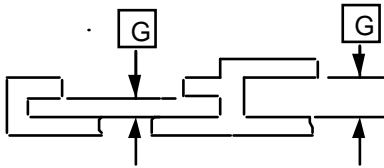


MINIMUM GAP SIZE

Do not specify gaps less than .060" as a jig must be placed inside of gap to support the legs. The wider the leg, the larger the gap should be as thicker jigs must be used for deeper gaps.

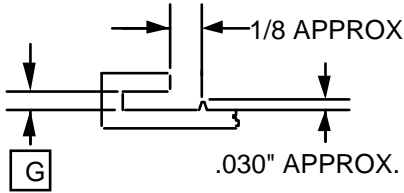

GAPS FOR THIN INSERTS

If paper or thin flexible inserts are used, set the gap at .060" and add a small thin bead as shown.

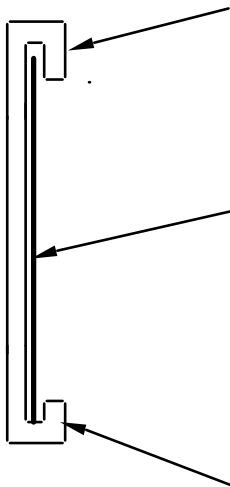

CONTROL OF OVERLAP


During development, if this leg is running short and the width of the slot is running toward the max., standard SPC practice is to lengthen this leg to insure sufficient overlap of the insert. If a minimum overlap is required, this should be specified.

INFORMATION ABOUT INSERT & REQUIRED FIT

Specify the width, thickness and material of the insert and indicate how it is to be inserted into the slot such as:


- Insert slides in from the end,
- Insert flexes and is inserted from the front,
- Insert must slide up into the top gap and then drop into the bottom gap.

The bottom leg can normally be shorter.

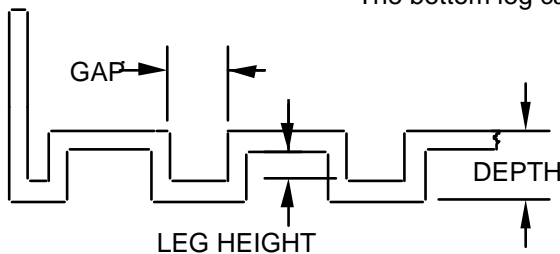

PROBLEMS WITH DEPTH & FLATNESS

This design makes it difficult to control the depth as the several leg heights won't be the same. This also makes it difficult to get flat bottom and top surfaces.

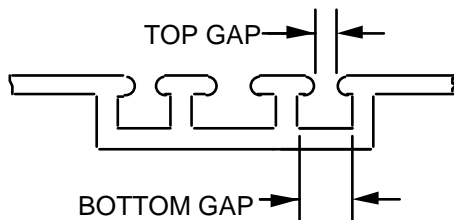


STACKED GAPS CAUSE PROBLEMS

This is an example of "Stacked Gaps". It is difficult to adjust the gap size, as whatever is done to the top gap usually affects the bottom gap. Larger tolerances may be required, especially if there are a series of gaps as shown. Changes in the adjacent gaps makes it difficult to control the gap dimension.

FIG. 7: GAP DESIGN

TABLE 4: ANGLE DESIGN TOLERANCES

<u>DIMENSION</u>	<u>NOMINAL DESIGN TOLERANCES</u> FOR THE FOLLOWING TYPES OF DIMENSIONS (SEE ILLUSTRATIONS BELOW)	
<u>LENGTH OF SHORT LEG</u> INCHES	<u>NORMAL TOLERANCES</u>	<u>TIGHT TOLERANCES</u>
	See FIG 8:ANGLE TOLERANCES below and FIG. 9: PROBLEMS IN MEASURING ANGLES on the next page.	Tight tolerances should only be used for simple shapes such as angles and channels. See FIG 8:ANGLE TOLERANCES below and FIG. 9: PROBLEMS IN MEASURING ANGLES on the next page.
	±	±
.25	5°	4°
.50	4°	3°
.75	3°	2°
1.0	2°	1.5°
1.5	2°	1.5°
2.0	1.5°	1°
3.0 & Up	1°	.75°

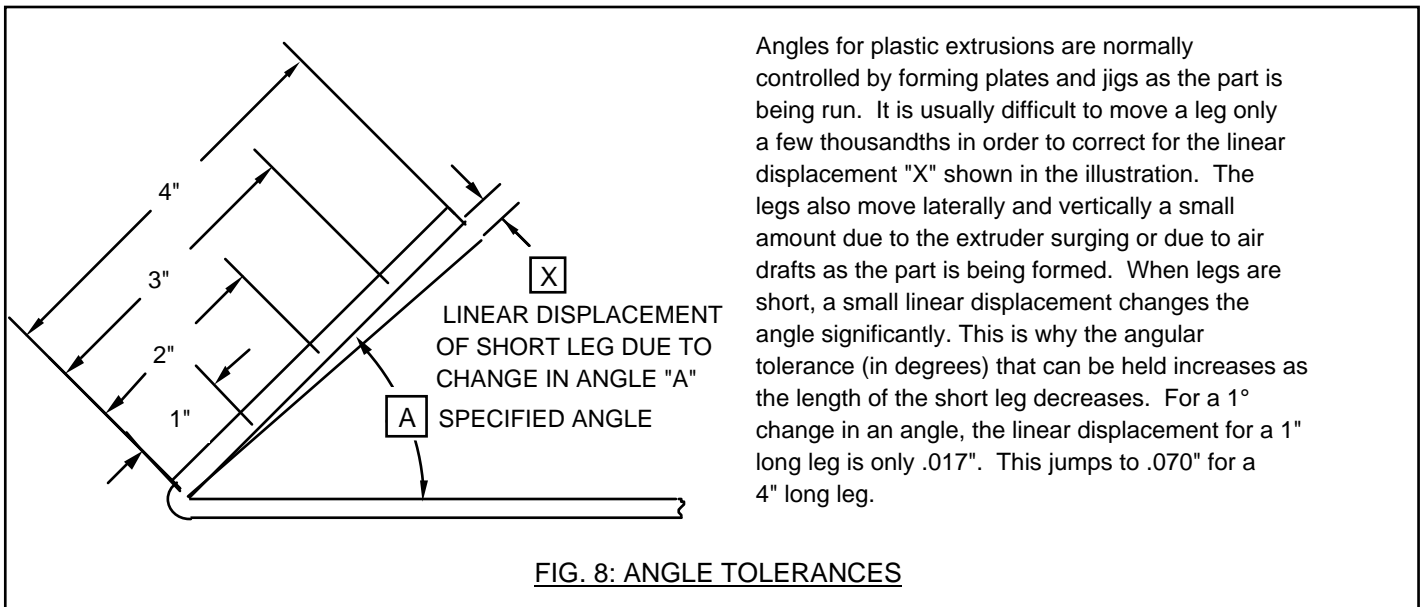

This is a drawing of a part. All the legs are perfectly straight and it is easy to measure the angles.

Sometimes it is better to use linear measurements as shown below to control angles.

The legs on plastic extrusions are not perfectly straight but are usually curved slightly as shown below. Note the difference in the measurement at "A" compared to that at "B". For all practical purposes, the angle between the legs is at 120° and the measurement at "A" is correct.



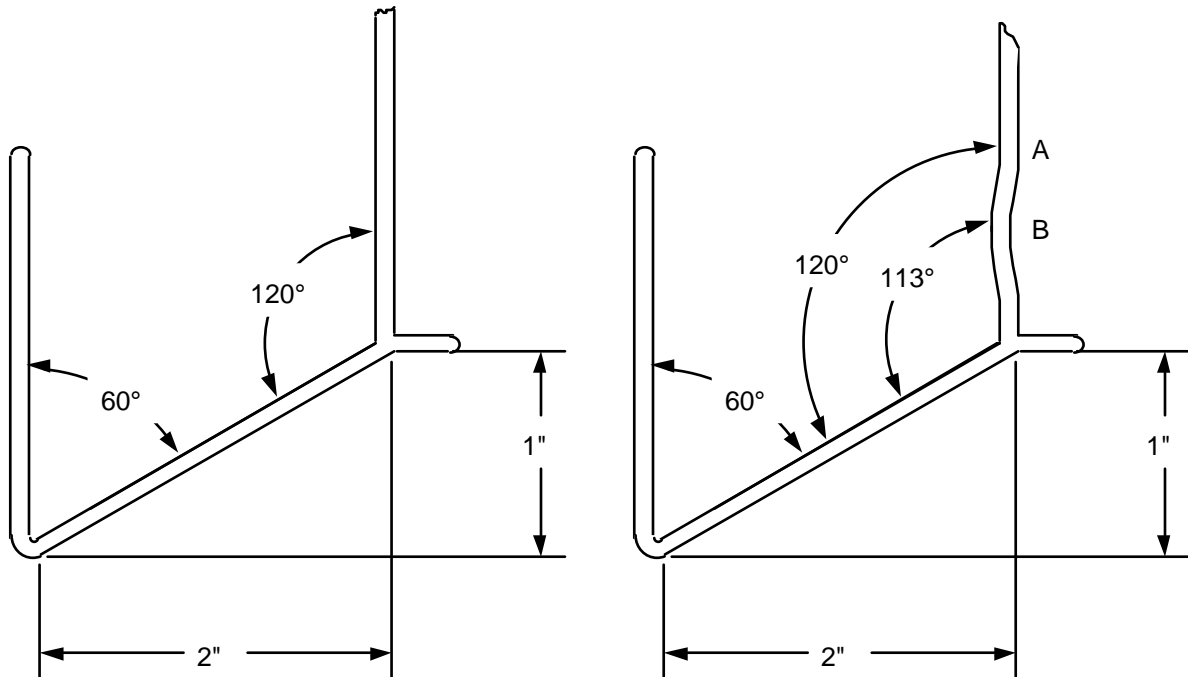


FIG. 9: PROBLEMS IN MEASURING ANGLES


TABLE 5: FABRICATION TOLERANCES

HOLE SIZE	+/- .008
EDGE TO FIRST HOLE	+/- .031
HOLE TO HOLE LOCATION	+/- .031
LAST HOLE TO EDGE	VARIABLES W/ LENGTH TOLERANCE
NOTCH WIDTH & HEIGHT	+/- .031

FIG. 10: DEGREES OF DIFFICULTY

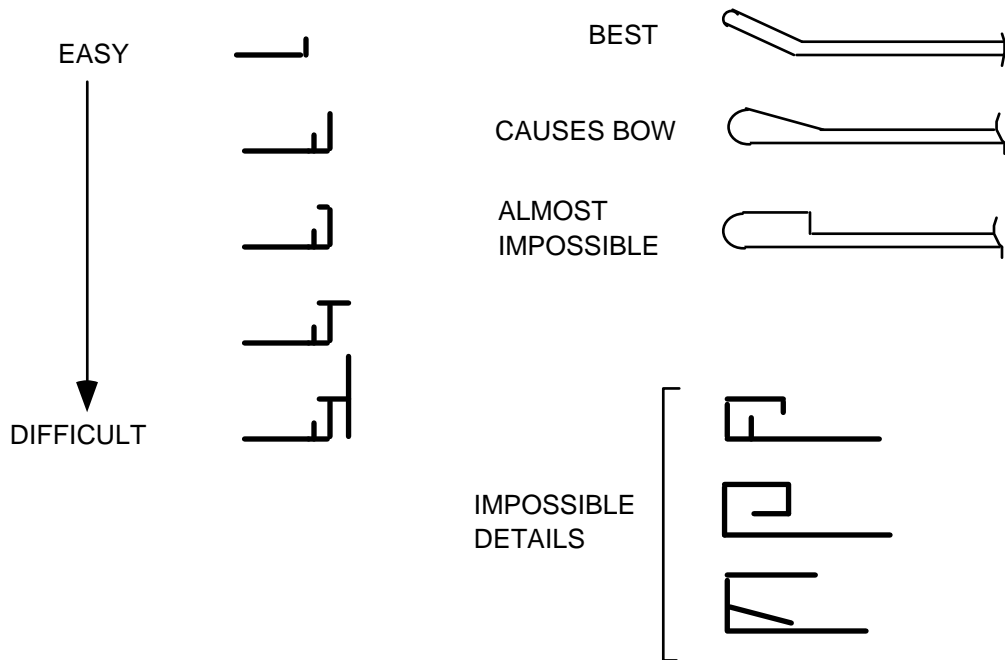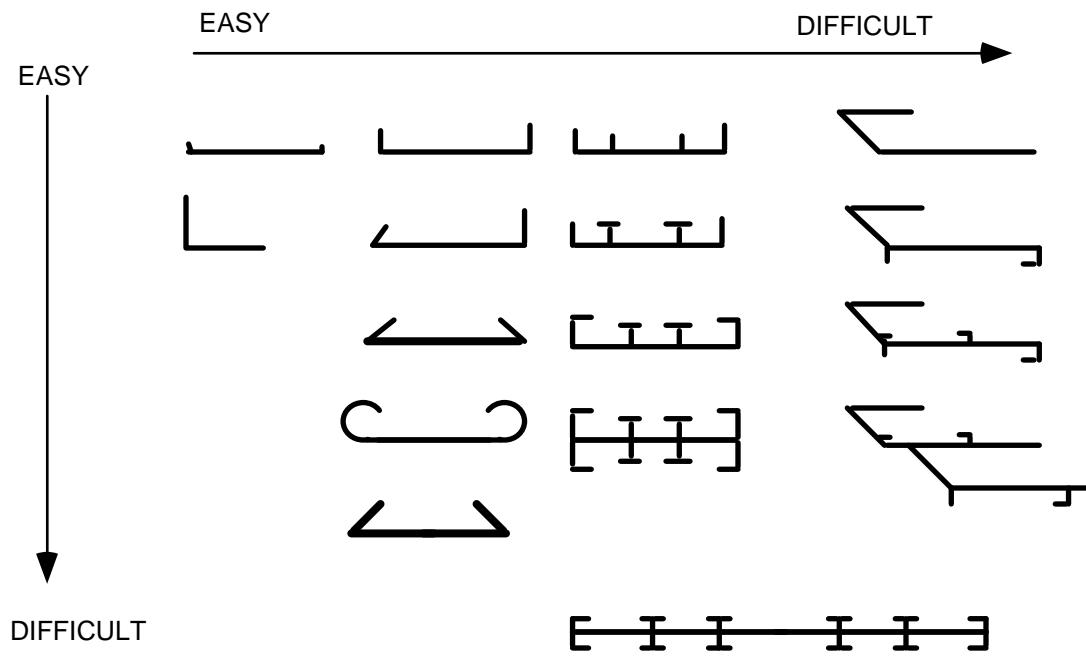


DIMENSIONING

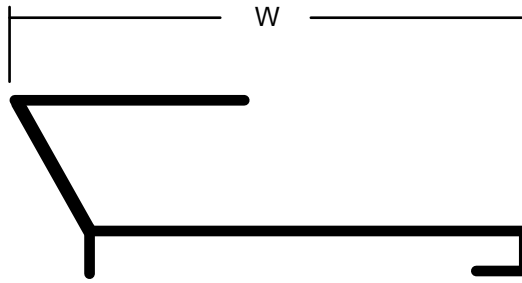


DIMENSION NOT PARALLEL TO POINTS BEING MEASURED

(OK FOR OVERALL DRAWING DIMENSION BUT DIFFICULT TO MEASURE)

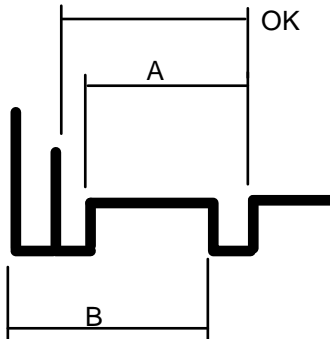


OUTSIDE TO INSIDE DIMENSIONS (A & B) DIFFICULT TO MEASURE

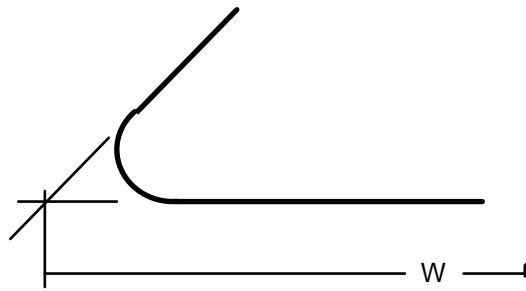

DIMENSIONS FROM INTERSECTION OF GEOMETRICAL POINTS

(DIMENSION OK AS REFERENCE DIMENSION BUT NOT MEASURABLE)

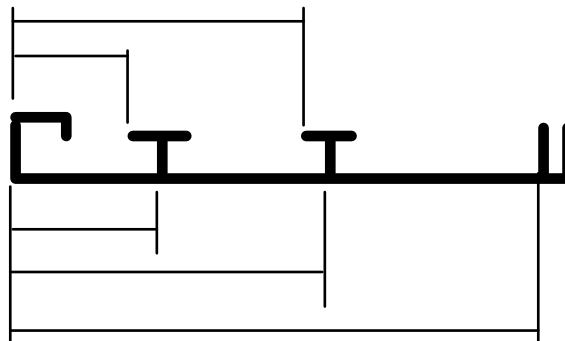

DATUM LINE DIMENSIONING

(NORMALLY CAN MEASURE, BUT NOT WHAT WANT TO MEASURE)

FACTORS AFFECTING TOLERANCES

- TOLERANCES DEPENDENT UPON COMPLEXITY OF THE PART
IF MANY SEGMENTS MORE DIFFICULT TO HOLD TOLERANCES
IF SIMPLE PART CLOSER TOLERANCES CAN BE HELD
- CHANGING PROCESS CONDITIONS
AMBIENT TEMPERATURE
CHANGES IN MATERIAL FROM BATCH TO BATCH
- OPERATOR DEPENDENT -- MANY MANUAL ADJUSTMENTS
- DIE DESIGN

GUIDELINES FOR USING TOLERANCE TABLES

- TOLERANCES ARE NOMINAL
- BEST TO USE DIMENSIONS THAT CAN BE MEASURED DIRECTLY
- START WITH DIMENSIONS AFFECTING FIT WITH MATING PARTS
- TRY TO LIMIT NUMBER OF DIMENSIONS WITH TOLERANCES
- USE REFERENCE DIMENSIONS WHERE POSSIBLE
SPC DEFINITION OF REFERENCE DIMENSION
REFERENCE DIMENSIONS USED IN DIE DESIGN
REFERENCE DIMENSION CHECKED DURING DEVELOPMENT

THICKNESS

- NORMALLY SPECIFY NOMINAL THICKNESS
EXPECT THICKNESS VARIATIONS
- NOMINALLY -- TO .090" \pm 10%, OVER .090" \pm 8%
- WHERE REQUIRED -- SPECIFY MIN OR MAX FOR PARTICULAR AREA

RADII

- NORMALLY NOT TRUE RADII --DIFFICULT TO MEASURE DIRECTLY
- USE RADIUS GAUGES WHEN NEED TO MEASURE
- WHEN TOLERANCES REQUIRED SEE TABLE 2 (SINGLE SEGMENT)

LENGTH

- NORMALLY \pm 1/16"
- FACTORS AFFECTING LENGTH CONTROL
LENGTH, LINE SPEED
CHANGE IN LENGTH DUE TO TEMPERATURE --SPC TO DESTINATION



Where Ideas Take Shape.

www.pexco.com